



James Woods
 Technical Services Department
 Toms Forest laboratory
 Toms Forest Quarry
 Kintore Inverurie
 Aberdeenshire: AB51 0YU

GRADATION ANALYSIS TEST REPORT
for Product: 1200/ 10/20mm Coarse Aggregate

Supplier/ source: DRY
 Material type: Drystone aggregate Test method: Wash grading to BS EN 933-1:2012

SAMPLE INFORMATION

Sample number **TOM_11007_A**

Sampled/ tested
 Mon 27 November 2023/ 28 11 23
 at 1100 hrs

Customer BNL PRODUCTION Full Destination
 Ticket <> Truck Reg - SampCert <> Chainage -
 Sampled by<>Operator R Leadbetter Weather Conditions
 Retest Samp Nos Data - Logged by D.MCRAE


SAMPLE ANALYSIS

Sieve size	Percent passing	Specification limits	Complies ?
40mm	100	100 - 100	yes
31.5mm	100	98 - 100	yes
25mm	100	-	-
20mm	96	85 - 99	yes
16mm	62	-	-
14mm	41	-	-
12.5mm	27	-	-
10mm	7	0 - 20	yes
8mm	2	-	-
6.3mm	2	-	-
5mm	1	-	-
4mm	1	0 - 5	yes
2.8mm	1	-	-
2mm	1	-	-
1mm	1	-	-
500µm	1	-	-
63µm	1	-	-
Moisture content %	1.2	not specified	-
Flakiness index	9	<=25	yes

Parameters are evaluated to the accuracy of spec. limits

REMARKS

Compliance status ok
 Category A of A-C excludes secondary parameters

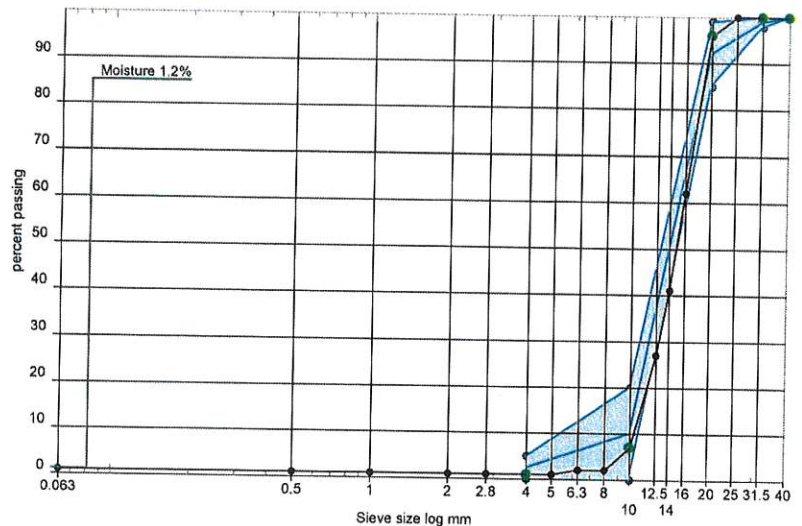

Signed D.McRae Senior Technician

Print date 19 Jan 2024