


GRADATION ANALYSIS TEST REPORT

Product: Golden Amber Gravel
 Material Code: BR14
 Supplied by: Breedon Quarry
 Customer:
 Site Address:
 Material type: Proprietary / Limestone



Sampled to: BS EN 932- 1: 1997
 Prepared to: BS EN 932- 2: 1999
 Test method: BS EN 933- 1: 2012

Sample number	1500
Ticket No	
Sampled by	Woodward
Date Sampled	23/04/2019
Sample location	Stockpile
Weather Conditions	

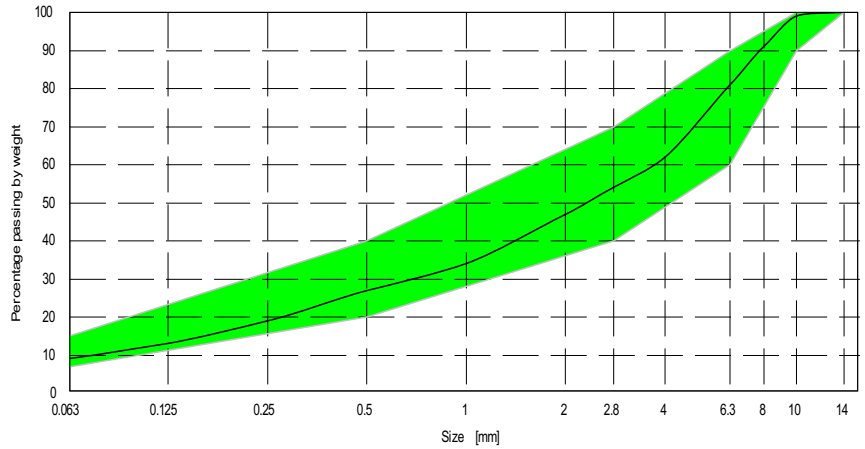

Sieve Size (mm)	Percent passing	Specification	Complies (Spec)	Control limits	Complies (Ctrl)
14	100	100 - 100	Yes	-	-
10	99	90 - 100	Yes	-	-
8	91	-	-	-	-
6.3	81	60 - 90	Yes	-	-
4	62	-	-	-	-
2.8	54	40 - 70	Yes	-	-
2	47	-	-	-	-
1	34	-	-	-	-
0.5	27	20 - 40	Yes	-	-
0.25	19	-	-	-	-
0.125	13	-	-	-	-
0.063	9.2	7.0 - 15.0	Yes	-	-
Moisture content (%)	2.2				
Uniformity Coefficient	49				

Sampled By: Woodward

Tested By: Healey

Date Tested: 23/04/2019